Role of vibrational entropy in the stabilization of the high-temperature phases of iron

Jürgen Neuhaus,[1,2] Michael Leitner,[1,2] Karl Nicolaus,[1] Winfried Petry,[1,2] Bernard Hennion,[3] and Arno Hiess[4]

[1] *Chair of Functional Materials, Physics Department, Technische Universität München, James-Franck-Str. 1, 85748 Garching, Germany*

[2] *Heinz Maier-Leibnitz Zentrum (MLZ), Technische Universität München, Lichtenbergstr. 1, 85748 Garching, Germany*

[3] *Laboratoire Léon Brillouin, CEA Saclay, 91191 Gif-sur-Yvette Cédex, France*

[4] *Institut Laue-Langevin, 38042 Grenoble, France, now at European Spallation Source AB, 22100 Lund, Sweden*

arXiv:1404.6459v1 [cond-mat.mtrl-sci] 25 Apr 2014

The phonon dispersions of the bcc and fcc phases of pure iron (α-Fe, γ-Fe and δ-Fe) at ambient pressure were investigated close to the respective phase transition temperatures. In the open bcc structure the transverse phonons along $T_1[\xi\xi 0]$ and $T_1[\xi\xi 2\xi]$ are of particularly low energy. The eigenvectors of these phonons correspond to displacements needed for the transformation to the fcc γ-phase. Especially these phonons, but also all other phonons soften considerably with increasing temperature. Comparing thermodynamic properties of the fcc and the two bcc phases it is shown that the high temperature bcc phase is stabilized predominantly by vibrational entropy, whereas for the stabilization of the fcc phase electronic entropy provides an equal contribution.

I. INTRODUCTION

The majority of metals crystallize from the melt in the open body-centered cubic structure, and the largest part of those transforms martensitically to a close-packed structure at lower temperatures. While the latter fact has been understood since a long time as the optimal solution to the electrostatic attraction between valence electrons and ionic cores subject to closed-shell repulsion[1], proposals to motivate the preference for the open structure at high temperatures have been controversial. The classical explanations due to Zener[2] and Friedel[3] identify the gain in vibrational entropy due to specific low-energy phonons to be responsible, a view which is shared by the majority of later numerical calculations[4–8] (but see Ref. 9 for a conflicting result). Direct experimental studies, where available, confirm the dominant contribution of vibrational entropy for the thermodynamic stability of bcc structures at high temperatures, e.g., for the transition metals of group 3 and 4[10–13], and the general necessity of considering the role of vibrations in the thermodynamics of materials, specifically at high temperatures, is recognized[14].

The polymorphism of iron, a system with strong magnetic interactions, is of particular interest in this context. Pure iron solidifies at 1811 K in the bcc δ-phase and undergoes a first transition to fcc γ-Fe at 1667 K. Very unusual, with decreasing temperature it transforms back to the bcc α-phase at 1185 K. Within the α-phase a magnetic transition occurs at 1043 K, below of which α-Fe is ferromagnetic[15].

The occurrence of the bcc α-phase is understood in the framework of band magnetism[16] as being due to ferromagnetic contributions to the total energy, which can be reproduced by density-functional calculations in the generalized-gradient approximation[17,18]. In contrast to the proposal of the 2γ-state model[19], the dominant view nowadays is that with the loss of magnetic correlations at higher temperatures a single paramagnetic fcc γ-phase results, as it corresponds to the non-magnetic structure of lowest total energy[17,20]. The small region of paramagnetic α-Fe is thought to be due to the persistence of local moments even above T_C[20,21].

More controversial are explanations for the $\gamma \rightarrow \delta$ transition, i.e., the question why Fe adopts again bcc in its high temperature phase. Published records of theoretical calculations focussing either purely on the electronic[16] or vibrational[6,22] contribution to the entropy generally find that the effect considered in the respective studies suffices for explaining the observed behaviour, while semi-empirical fits to experimental data[19,23] favor electronic reasons (but see Ref. 23 for an overview of the widely differing assumptions in such approaches). Part of the interest in the δ-phase is due to the fact that a paramagnetic bcc structure with reduced lattice constant is also proposed for the earth inner core, stabilized by vibrational entropy[24–27].

By measuring the phonon dispersion of δ-Fe for the first time together with temperature-dependent dispersions for α- as well as γ-Fe we are able to determine the vibrational entropy of the distinct ambient-pressure iron phases purely from experiment and to evaluate the role of vibrational entropy in stabilizing the high-temperature phases.

II. EXPERIMENTAL DETAILS

Several large single crystals of the δ-phase with a typical size of 40 to 50 mm in length and 10 mm in diameter were grown from high purity (4N) Fe rods by the zone melting technique using our combined single crystal growth and measuring furnace[28]. After the *in-situ* growth on the three-axis spectrometer they were kept continuously above the transition temperature $T_{\gamma\leftrightarrow\delta}$. To suppress evaporation of the sample over the course of the measurement (the evaporation rate under vacuum at 1743 K was estimated to 20 g/h) a high purity Argon atmosphere of 700 mbar was used. The temperature could be stabilized within $\pm$5 K with a gradient along the single

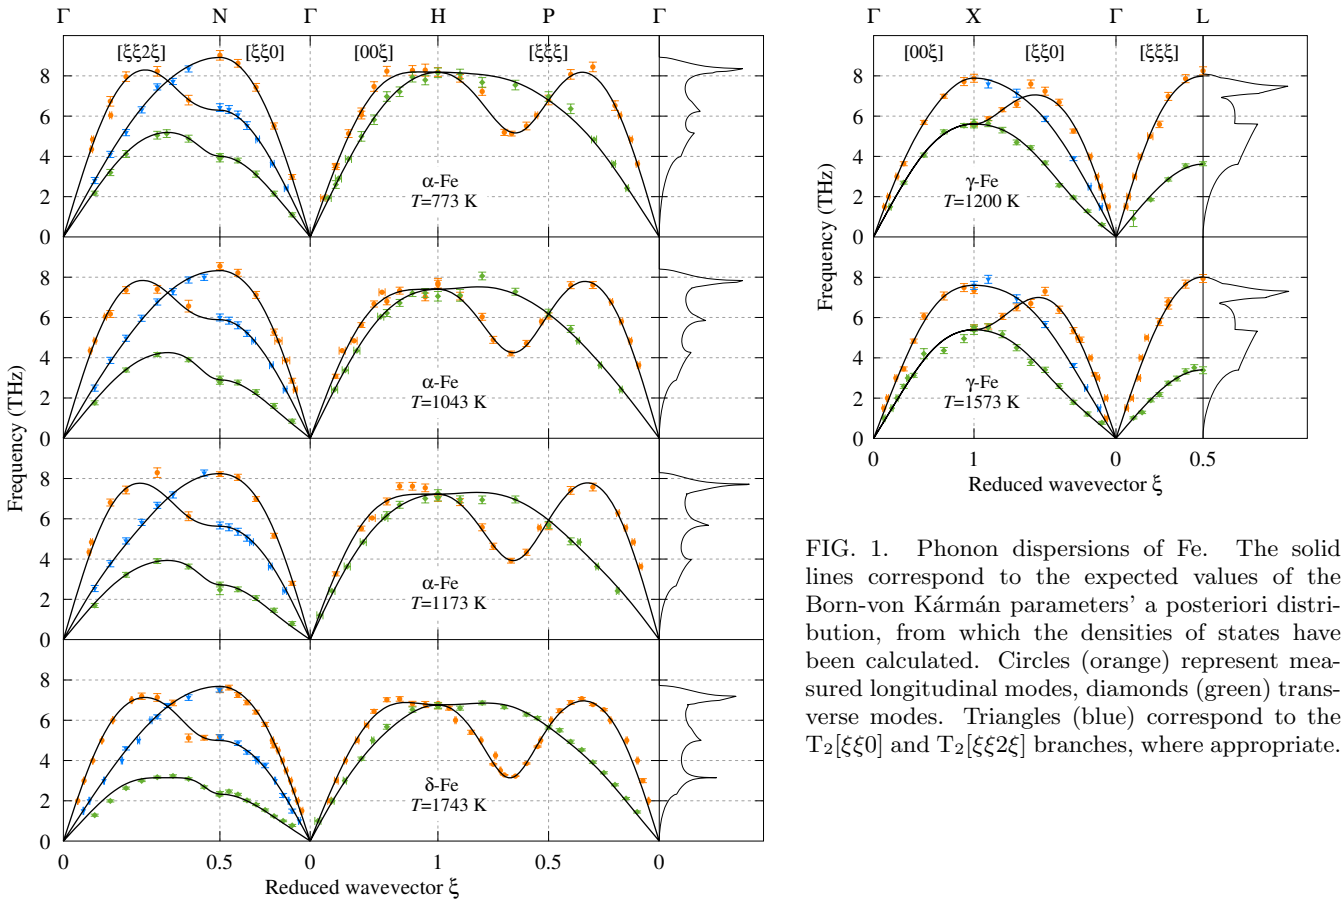

FIG. 1. Phonon dispersions of Fe. The solid lines correspond to the expected values of the Born-von Kármán parameters' a posteriori distribution, from which the densities of states have been calculated. Circles (orange) represent measured longitudinal modes, diamonds (green) transverse modes. Triangles (blue) correspond to the $T_2[\xi\xi 0]$ and $T_2[\xi\xi 2\xi]$ branches, where appropriate.

crystalline part of the sample of about 15 K. The absolute temperature was calibrated by the known transition temperatures $T_{\alpha\leftrightarrow\gamma}$ and $T_{\gamma\leftrightarrow\delta}$.

High purity single crystals of the α-phase with 5.5 mm in diameter and variable length were grown by recrystallization at the Max-Planck-Institut für Metallforschung, Stuttgart. A standard resistance furnace has been used to heat the crystals under vacuum with an accuracy of ± 8 K. Heating these α-Fe single crystals into the γ-phase transformed them to a nearly perfect *powder* (polycrystalline) sample. However, cycling approximately ten times through the α-γ transition finally led to the growth of a 3 cm^3 γ-single crystal by recrystallization.

The measurements in the δ-phase were performed at the three-axis spectrometer 1T at the LLB, Saclay, in the α-phase at spectrometer E7 at the HMI, Berlin and those in the γ-phase at spectrometer IN3 at the ILL, Grenoble. For all measurements a pyrolytic graphite monochromator and analyzer were used in constant final wave-vector mode.

III. PHONON DISPERSIONS

The phonon dispersions of bcc iron were measured at 773 K, 1043 K, 1173 K (preliminarily published in Ref. 29) and 1743 K. In the γ-phase experiments were done at 1200 K and 1573 K. All measurements cover the main symmetry directions and, for the bcc phases, additionally the $[\xi\xi 2\xi]$ direction. The obtained phonon frequencies are presented in figure 1 (see the supplemental material[30] for the data). Within the bcc-phases a softening of the entire phonon dispersion is observed when passing from room temperature (cp. Refs. 31–35) to $T_{\alpha\leftrightarrow\gamma}$. Most pronounced, however, is the decrease of the transverse branches $T_1[\xi\xi 2\xi]$ and $T_1[\xi\xi 0]$, reducing to a value of 53% at the zone boundary in the δ-phase compared to room temperature. This softening has a nonlinear temperature dependence, particularly around the ferromagnetic transition as observed earlier[36,37]. Interestingly, recent finite-temperature ab-initio calculations show that a variety of independent phenomena can give rise to this effect: dynamical mean-field theory[38] (treating electronic excitations), density-functional theory under disordered local moment paramagnetism[39] as well as self-consistent lattice dynamics[27] (treating anharmonic effects) agree that the softening with temperature is strongest for this branch. Our data also display an increase of the linewidth of these phonons with increasing temperature in the order of 0.1 THz, however the damping of transverse phonons in the α-phase is considerably smaller than in the δ-phase.

Concerning phonon anomalies, i.e., low frequencies and strong damping along $T_1[\xi\xi 0]$ and $T_1[\xi\xi 2\xi]$, the dispersion of δ-Fe resembles to the high temperature

TABLE I. Force constants in N/m estimated by Bayesian inference from the phonon dispersion of Fe at various temperatures in the bcc phases with a Born-von Kármán model taking into account interactions up to the fifth neighbour shell.

	773 K	1043 K	1173 K	1743 K
$\Phi_{\mathrm{L}}^{[111]}$	44.53 (49)	41.99 (37)	41.23 (36)	35.95 (21)
$\Phi_{\mathrm{T}}^{[111]}$	1.10 (68)	-1.99 (50)	-3.35 (49)	-2.76 (24)
$\Phi_{\mathrm{L}}^{[200]}$	11.44 (90)	7.50 (62)	7.51 (61)	9.34 (37)
$\Phi_{\mathrm{T}}^{[200]}$	0.18 (46)	0.65 (34)	-0.14 (34)	-0.98 (19)
$\Phi_{\mathrm{L}}^{[220]}$	2.91 (42)	2.72 (33)	3.20 (31)	0.85 (16)
$\Phi_{\mathrm{T}[1\bar{1}0]}^{[220]}$	-0.27 (31)	-0.04 (25)	-0.48 (25)	1.07 (10)
$\Phi_{\mathrm{T}[001]}^{[220]}$	-0.60 (45)	-0.16 (34)	0.27 (35)	-0.87 (24)
$\Phi_{xx}^{[311]}$	-0.15 (22)	0.12 (16)	0.19 (17)	-0.18 (10)
$\Phi_{yy}^{[311]}$	-0.07 (15)	-0.13 (12)	0.12 (11)	0.25 (7)
$\Phi_{yz}^{[311]}$	-0.16 (21)	-0.24 (16)	-0.33 (16)	-0.22 (5)
$\Phi_{xy}^{[311]}$	-0.09 (15)	0.24 (12)	0.34 (11)	0.22 (4)
$\Phi_{\mathrm{L}}^{[222]}$	0.50 (26)	0.50 (22)	0.47 (21)	1.56 (11)
$\Phi_{\mathrm{T}}^{[222]}$	-0.34 (47)	0.13 (36)	0.18 (34)	-0.40 (18)

TABLE II. Force constants in N/m estimated by Bayesian inference from the phonon dispersion of Fe at various temperatures in the fcc phases with a Born-von Kármán model taking into account interactions up to the fifth neighbour shell.

	1200 K	1573 K
$\Phi_{\mathrm{L}}^{[110]}$	30.16 (37)	29.84 (41)
$\Phi_{\mathrm{T}[1\bar{1}0]}^{[110]}$	-2.27 (48)	-2.16 (48)
$\Phi_{\mathrm{T}[001]}^{[110]}$	0.18 (79)	-1.26 (83)
$\Phi_{\mathrm{L}}^{[200]}$	-1.90 (74)	-0.21 (74)
$\Phi_{\mathrm{T}}^{[200]}$	0.34 (35)	0.15 (35)
$\Phi_{xx}^{[211]}$	0.18 (28)	0.61 (29)
$\Phi_{yy}^{[211]}$	-0.01 (19)	-0.04 (20)
$\Phi_{yz}^{[211]}$	0.24 (17)	0.27 (17)
$\Phi_{xy}^{[211]}$	0.41 (10)	0.35 (12)
$\Phi_{\mathrm{L}}^{[220]}$	0.85 (30)	0.71 (30)
$\Phi_{\mathrm{T}[1\bar{1}0]}^{[220]}$	0.14 (32)	0.25 (32)
$\Phi_{\mathrm{T}[001]}^{[220]}$	-0.01 (43)	-0.21 (43)
$\Phi_{xx}^{[310]}$	0.27 (13)	-0.22 (14)
$\Phi_{yy}^{[310]}$	0.05 (22)	-0.32 (23)
$\Phi_{zz}^{[310]}$	-0.19 (24)	0.07 (24)
$\Phi_{xy}^{[310]}$	0.14 (20)	-0.30 (21)

phases of group 3 (including some lanthanides) and 4 metals[10–12,40–42]. These anomalies are indicative for latent instabilities towards a transition to a close-packed structure[13]. As in the case of La and Ce, Fe transforms to the fcc structure, in contrast to the other group 3 and 4 metals, which transform to hcp. The resulting stacking sequence of close-packed planes necessitates long-wavelength shears, with the corresponding shear constant $C' = 1/2(C_{11} - C_{12})$ given by the initial slope of the $\mathrm{T}_1[\xi\xi 0]$ phonon branch. Indeed, Table III shows that the cubic anisotropy parameter $A = C_{44}/C'$ (i.e., the squared ratio of the small-q slopes of the $[\xi\xi 0]$ acoustic branches), which has values below 6 in the elements transforming to hcp[10,11,41], reaches up to around 10 for Fe, La[13] and Ce[42], analogous to the criteria put forward in Ref. 43. For comparison, Cr[44] and Nb[45], which display the bcc structure over the whole range, have an anisotropy parameter on the order of one. The most remarkable point concerning the γ-phase dispersions is the positive curvature of the $\mathrm{T}_1[\xi\xi 0]$ branch, which reproduces the findings of Zarestky and Stassis[46].

IV. DATA MODELLING AND BORN-VON KÁRMÁN PARAMETERS

For deducing further quantitative information we describe the measured phonon dispersions by a Born-von Kármán model (corresponding to the quasi-harmonic assumption). In order to obtain methodically rigorous uncertainties of the estimated quantities, we followed Bayesian inference and generated samples of the Born-von Kármán force constants including interactions up to the fifth nearest neighbor shell for each measured phonon dispersion. We computed the likelihood directly from the experimentally estimated errors. As the information contained in measurements of the high-symmetry directions alone is limited (see for example the pertinent discussion in Ref. 47), we used a prior distribution that penalizes high values of the force constants for far shells and non-central forces, as dictated by physical understanding (see supplemental material[30]).

Phonon dispersions corresponding to the resulting expected values of the force constants are shown in figure 1 as solid lines, while an illustration of the uncertainties is given in the supplemental material[30]. The Born-von Kármán force constants (mean and standard deviation) are summarized in Tabs. I and II for the bcc and fcc measurements, respectively. For those sites that are along high-symmetry directions relative to the central atom, we parametrized the model directly in terms of longitudinal and transversal force constants, that is in terms of the eigenvalues of the Jacobi matrices of the forces, while for lower-symmetry shells we give the independent entries with respect to the Cartesian basis of the Jacobi matrices. The parameters for the respective shells' other sites follow by symmetry.

The behaviour of the determined BvK-parameters is quite plausible: As expected, the dominant interactions are short-range and of longitudinal nature, while most of the interactions over longer ranges are individually not significantly different from zero (collectively, they are significant, however; setting all of them to zero would give noticeably worse fits). Apart from the softening of the nearest-neighbour longitudinal interaction with temper-

ature, the most striking effect is the behaviour of $\Phi_{\mathrm{T}}^{[111]}$ in the bcc phases: its becoming negative with increasing temperature is the main reason for the softening of the $\mathrm{T}_1[\xi\xi 0]$ branch. As this happens around the Curie temperature, it is most probably of magnetic origin and pinpoints the instability of the body-centered lattice with loss of magnetism. Note that the δ-phase's comparatively larger long-range BvK-parameters should not be over-interpreted, as they are due to the better statistics of this one measurement (also reflected in the smaller uncertainties).

The generated samples of parameter sets can be used to directly compute thermodynamic quantities. By virtue of this approach, we can quote well-defined estimated errors for the computed quantities that follow directly from the errors of the experimental data points, subject only to the assumption of the Born-von Kármán model and the chosen prior distribution. Figure 1 demonstrates that we do not over-regularize our data, therefore we are confident that our quoted estimated errors are conservative.

The phonon densities of states for each of the measured temperatures as calculated from the force constants by the tetrahedron method[48,49] are given to the right of the phonon dispersions in figure 1. They show that, according to the model, the softening is not limited to the measured high-symmetry directions, but spans the whole reciprocal space. Note that the spike appearing slightly above 3 THz in the δ-phase is due to the flattening of the $\mathrm{T}_1[\xi\xi 2\xi]$ branch.

V. THERMODYNAMIC QUANTITIES

For settling the question for the reason of the existence of the δ-phase by experiment we computed the distinct thermodynamic quantities related to the phase transitions. The most evident way to report our results is by way of Debye temperatures: We define Θ_U for a given temperature T so that the internal energy of the Born-von Kármán model corresponding to the measured dispersion coincides with the internal energy of the Debye model with Θ_U as characteristic temperature. Θ_S is defined analogously via the entropy[50]. The resulting values are given in Table III. As the temperatures of measurement are much larger than Θ_i, the harmonic assumption would imply constant Debye temperatures. This is clearly not the case; the phonon softening discussed above leads to decreasing Debye temperatures with increasing temperature. Moreover, a fit with a phenomenological model for the respective structures (see the supplemental material[30] for a detailed discussion) given in figure 2 implies that Θ_S is discontinuous at the phase transitions, which is to be expected for a first-order transition. Our measurements constitute the first experimental determination of the Debye temperature for the high-temperature δ-phase (cp. Ref. 23 for the previous uncertainties).

The recommended values for the experimental total

T (K)	Θ_U (K)	Θ_S (K)	C_{11} (GPa)	C_{44} (GPa)	C' (GPa)	A
773	399.0(15)	398.5(15)	212(8)	112(5)	37(4)	3.1(4)
1043	363.6(15)	358.5(15)	189(7)	107(4)	16(3)	7.0(16)
1173	354.5(11)	348.2(12)	190(7)	118(5)	12(3)	10.7(33)
1200	345.3(19)	342.8(19)	188(5)	87(3)	16(2)	5.7(9)
1573	333.5(24)	329.5(23)	171(5)	68(3)	18(2)	3.8(6)
1743	324.1(7)	316.6(6)	158(4)	86(2)	11(1)	8.2(6)

TABLE III. Various properties deduced from the Born-von Kármán parameters for the respective temperatures: The Debye temperatures defined via internal energy (Θ_U) and entropy (Θ_S), the three cubic elastic constants and the anisotropy coefficient.

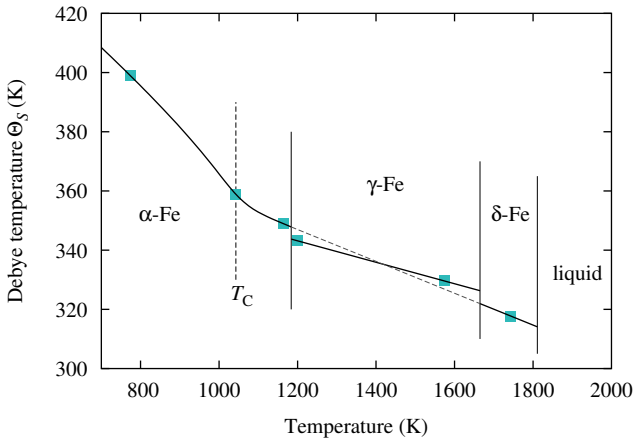

FIG. 2. Debye temperature defined via the vibrational entropy as a function of temperature. The errors are smaller than the symbols.

latent heat are $\Delta U_{\mathrm{tot}}^{\alpha\to\gamma} = T\Delta S_{\mathrm{tot}}^{\alpha\to\gamma} = 0.091\,k_{\mathrm{B}}T/\mathrm{atom}$ and $\Delta U_{\mathrm{tot}}^{\gamma\to\delta} = 0.060\,k_{\mathrm{B}}T/\mathrm{atom}$[15]. Extrapolating our data to the transition temperatures gives the respective contributions of the vibrational entropies as $\Delta S_{\mathrm{vib}}^{\alpha\to\gamma} = 0.038(19)\,k_{\mathrm{B}}/\mathrm{atom}$ and $\Delta S_{\mathrm{vib}}^{\gamma\to\delta} = 0.055(22)\,k_{\mathrm{B}}/\mathrm{atom}$. In contrast, the differences in internal vibrational energy are only $\Delta U_{\mathrm{vib}}^{\alpha\to\gamma} = 0.007(2)\,k_{\mathrm{B}}T/\mathrm{atom}$ and $\Delta U_{\mathrm{vib}}^{\gamma\to\delta} = 0.002(2)\,k_{\mathrm{B}}T/\mathrm{atom}$. These figures show that at the $\alpha\to\gamma$ transition about $\Delta U_{\mathrm{elec}} = \Delta U_{\mathrm{tot}} - \Delta U_{\mathrm{vib}} = 0.08\,k_{\mathrm{B}}T = 9\,\mathrm{meV}$ per atom are taken up by the electronic system, as the bcc-phase is energetically still stabilized by magnetic fluctuations. This increase in internal energy is compensated by an increase in entropy, to which the phononic subsystem contributes slightly less than half of the value, the rest being made up by electronic contributions (due to the loss of correlations). At the $\gamma\to\delta$ transition the situation is different: due to the increased temperature, the stabilizing effect of the magnetic fluctuations is lost, and the high-temperature phase again costs in internal electronic energy ($\Delta U_{\mathrm{tot}} \approx \Delta U_{\mathrm{elec}} = 0.06 k_{\mathrm{B}}T$ per atom). Comparing

our deduced value of $\Delta S_{\rm vib} = 0.055\,k_{\rm B}$/atom with the total entropy difference of $\Delta S_{\rm tot} = 0.060\,k_{\rm B}$/atom shows that this transition is now driven nearly exclusively by the increased vibrational entropy of the open bcc structure. The smallness of the electronic contribution to the entropy is probably due to the electronic structures of both phases being only weakly correlated. Note that our determination of $\Delta S_{\rm vib}^{\gamma\to\delta}$ probably even underestimates the actual value, as in the high-temperature bcc phases typically a hardening of selected phonons with increasing temperature is found, resulting in *increasing* Debye temperatures[11].

VI. CONCLUSIONS

In conclusion we find, by measuring for the first time the phonon response in the high temperature bcc phase of Fe, that the stabilization of the δ-phase is due to the vibrational entropy of transverse phonons of particular low energy, favoring the picture of a first order transition driven by vibrational entropy[51–53]. This result is in full accordance with what we have found for the bcc phases in the nonmagnetic group 3 and 4 metals, but is more surprising for δ-Fe, where magnetic fluctuations have been suspected to stabilize the body-centered cubic phase[16]. Note that also the high-temperature bcc phase of Ce, another example of a system with a complex phase diagram due to magnetic interactions, has experimentally been found to be stabilized by vibrational entropy[42,54], giving weight to the hypothesis that *in general*, the existence of high-temperatur bcc phases is due to vibrational entropy.

For the low temperature bcc structure of Fe we find that magnetic contributions establish the ferromagnetic ground state and are responsible for the structural change in the paramagnetic regime, but also for this transition there is a significant vibrational contribution to stabilize fcc-Fe.

ACKNOWLEDGMENTS

We would like to thank E. Günther and U. Eßmann from the Max-Planck-Institut für Metallforschung, Stuttgart, for providing the α-Fe single crystals, A. Krimmel for assistance during the measurements at the HMI, Berlin, and I. Leonov and D. Vollhardt for discussions and communication of theoretical results. Financial support of the LLB by the HCM program under contract No. ERB CHGECT 920001 and DFG under project PE580/3-1 and the Collaborative Research Center TRR 80 are acknowledged.

NOTE ADDED IN PROOF

After acceptance of this paper, a theoretical work on the basis of dynamical mean-field theory was reported[55], which confirms our interpretation.

[1] K. Fuchs, Proc. R. Soc. Lond. A **151**, 585 (1935).
[2] C. Zener, Phys. Rev. **71**, 846 (1947).
[3] J. Friedel, J. Physique Lett. **35**, 59 (1974).
[4] Y.-Y. Ye, Y. Chen, K.-M. Ho, B. N. Harmon, and P.-A. Lindgård, Phys. Rev. Lett. **58**, 1769 (1987).
[5] S. Rubini and P. Ballone, Phys. Rev. B **48**, 99 (1993).
[6] Y. N. Osetsky and A. Serra, Phys. Rev. B **57**, 755 (1998).
[7] X. Dai, S. Y. Savrasov, G. Kotliar, A. Migliori, H. Ledbetter, and E. Abrahams, Science **300**, 953 (2003).
[8] P. Souvatzis, O. Eriksson, M. I. Katsnelson, and S. P. Rudin, Phys. Rev. Lett. **100**, 095901 (2008).
[9] F. Willaime and C. Massobrio, Phys. Rev. Lett. **63**, 2244 (1989).
[10] W. Petry, A. Heiming, J. Trampenau, M. Alba, C. Herzig, H. R. Schober, and G. Vogl, Phys. Rev. B **43**, 10933 (1991).
[11] A. Heiming, W. Petry, J. Trampenau, M. Alba, C. Herzig, H. R. Schober, and G. Vogl, Phys. Rev. B **43**, 10948 (1991).
[12] F. Güthoff, W. Petry, C. Stassis, A. Heiming, B. Hennion, C. Herzig, and J. Trampenau, Phys. Rev. B **47**, 2563 (1993).
[13] W. Petry, J. Phys. IV **05**, C2-15 (1995).
[14] B. Fultz, Prog. Mater. Sci. **55**, 247 (2010).
[15] Q. Chen and B. Sundman, J. Phase Equilibria **22**, 631 (2001).
[16] H. Hasegawa and D. G. Pettifor, Phys. Rev. Lett. **50**, 130 (1983).
[17] D. J. Singh, W. E. Pickett, and H. Krakauer, Phys. Rev. B **43**, 11628 (1991).
[18] H. C. Herper, E. Hoffmann, and P. Entel, Phys. Rev. B **60**, 3839 (1999).
[19] L. Kaufman, E. V. Clougherty, and R. J. Weiss, Acta Metall. **11**, 323 (1963).
[20] I. Leonov, A. I. Poteryaev, V. I. Anisimov, and D. Vollhardt, Phys. Rev. Lett. **106**, 106405 (2011).
[21] V. I. Anisimov, A. S. Belozerov, A. I. Poteryaev, and I. Leonov, Phys. Rev. B **86**, 035152 (2012).
[22] L. Sandoval, H. M. Urbassek, and P. Entel, Phys. Rev. B **80**, 214108 (2009).
[23] G. Grimvall, Phys. Scr. **13**, 59 (1976).
[24] C. S. Yoo, N. C. Holmes, M. Ross, D. J. Webb, and C. Pike, Phys. Rev. Lett. **70**, 3931 (1993).
[25] L. Vočadlo, D. Alfè, M. J. Gillan, I. G. Wood, J. P. Brodholt, and G. D. Price, Nature (London) **424**, 536 (2003).
[26] A. B. Belonoshko, R. Ahuja, and B. Johansson, Nature (London) **424**, 1032 (2003).
[27] W. Luo, B. Johansson, O. Eriksson, S. Arapan, P. Souvatzis, M. I. Katsnelson, and R. Ahuja, Proc. Natl. Acad. Sci. USA **107**, 9962 (2010).
[28] T. Flottmann, W. Petry, R. Serve, and G. Vogl, Nucl. Instrum. Methods A **260**, 165 (1987).
[29] J. Neuhaus, W. Petry, and A. Krimmel, Physica B **234–236**, 897 (1997).

[30] See Supplemental Material at [URL will be inserted by publisher] for experimental data and additional discussion.

[31] B. N. Brockhouse, H. E. Abou-Helal, and E. D. Hallman, Solid State Commun. **5**, 211 (1967).

[32] J. Bergsma, C. van Dijk, and D. Tocchetti, Phys. Lett. A **24**, 270 (1967).

[33] V. J. Minkiewicz, G. Shirane, and R. Nathans, Phys. Rev. **162**, 528 (1967).

[34] C. van Dijk and J. Bergsma, in *Proceeding of a Symposium, IAEA, Vienna* (1968), vol. 1, p. 233.

[35] S. Klotz and M. Braden, Phys. Rev. Lett. **85**, 3209 (2000).

[36] A. M. de Vallêra, Ph.D. thesis, Cambridge (1977).
A. M. de Vallêra, J. Phys. Colloques **42**, C6-398 (1981).

[37] S. K. Satija, R. P. Comès, and G. Shirane, Phys. Rev. B **32**, 3309 (1985).

[38] I. Leonov, A. I. Poteryaev, V. I. Anisimov, and D. Vollhardt, Phys. Rev. B **85**, 020401 (2012).

[39] F. Körmann, A. Dick, B. Grabowski, T. Hickel, and J. Neugebauer, Phys. Rev. B **85**, 125104 (2012).

[40] J. Trampenau, A. Heiming, W. Petry, M. Alba, C. Herzig, W. Miekeley, and H. R. Schober, Phys. Rev. B **43**, 10963 (1991).

[41] W. Petry, J. Trampenau, and C. Herzig, Phys. Rev. B **48**, 881 (1993).

[42] K. Nicolaus, J. Neuhaus, W. Petry, and J. Bossy, Eur. Phys. J. B **21**, 357 (2001).

[43] J. M. Wills, O. Eriksson, P. Söderlind, and A. M. Boring, Phys. Rev. Lett. **68**, 2802 (1992).

[44] J. Trampenau, W. Petry, and C. Herzig, Phys. Rev. B **47**, 3132 (1993).

[45] F. Güthoff, B. Hennion, C. Herzig, W. Petry, H. R. Schober, and J. Trampenau, J. Phys.: Condens. Matter **6**, 6211 (1994).

[46] J. Zarestky and C. Stassis, Phys. Rev. B **35**, 4500 (1987).

[47] E. C. Svensson, B. N. Brockhouse, and J. M. Rowe, Phys. Rev. **155**, 619 (1967).

[48] G. Lehmann, P. Rennert, M. Taut, and H. Wonn, Phys. Status Solidi **37**, K27 (1970).
G. Lehmann and M. Taut, Phys. Status Solidi B **54**, 469 (1972).

[49] O. Jepson and O. K. Anderson, Solid State Commun. **9**, 1763 (1971).

[50] H. R. Schober and P. H. Dederichs, in *Metals: Phonon States, Electron States and Fermi Surfaces*, edited by K.-H. Hellwege and J. L. Olsen (Springer, Berlin, Heidelberg, New York, 1981), vol. 13a of *Landolt-Börnstein New Series — Group III Condensed Matter*.

[51] J. A. Krumhansl and R. J. Gooding, Phys. Rev. B **39**, 3047 (1989).

[52] W. C. Kerr and M. J. Rave, Phys. Rev. B **48**, 16234 (1993).

[53] P. Mohn, K. Schwarz, and P. Blaha, J. Phys.: Condens. Matter **8**, 817 (1996).

[54] M. E. Manley, R. J. McQueeney, J. L. Robertson, B. Fultz, and D. A. Neumann, Phil. Mag. Lett. **80**, 591 (2000).

[55] I. Leonov, A. I. Poteryaev, Y. N. Gornostyrev, A. I. Lichtenstein, M. I. Katsnelson, V. I. Anisimov, and D. Vollhardt (2014), arXiv:1403.6497 [cond-mat.str-el].